

RESISTANCE SPOT WELDING OF BLUESCOPE STEEL METALLIC-COATED STEEL SHEET

TECHNICAL BULLETIN TB-21

Rev 4, November 2004

This issue supersedes all previous issues

INTRODUCTION

High volume welding industries require simple and cost effective joining technology for thin steel sheet. Resistance spot welding meets these requirements and is also adaptable in that it can be easily incorporated with robotic systems. In the past, spot welding parameter selection, was considered relatively simple for uncoated steel but the range of metallic-coated steels now available as superior replacement products means parameter selection is far more critical.

While it is possible to achieve many thousands of welds from one set of electrodes employed on an uncoated steel before replacement or redressing of electrodes is necessary, features of individual metallic coated steel coatings means as little as 250 welds may only be possible if inappropriate parameters are chosen.


The information presented in this Technical Bulletin is a result of a number of detailed weldability studies on the more commercially available electrode chemistries used in conjunction with those metallic coated steels most commonly spot welded, namely ZINCALUME[®] zinc/aluminium alloy-coated steel, GALVABOND[®] zinc-coated steel ZINCANNEAL[®] zinc/iron alloy-coated steel and ZINCSEAL[®] zinc/iron alloy-coated steel.

THE MECHANISM OF ELECTRODE DEGRADATION

The rate of degradation of resistance spot welding electrodes during welding of metallic coated steels is far greater than that experienced during welding of uncoated steels. Due to the lower contact resistances of zinc coatings, welding times and current levels are required to be higher in order to produce satisfactory weld sizes. This provides the driving force for alloying to take place between the electrode working face and the metallic coating. The conventional truncated cone electrode tip diameter (see Figure 1) increases as welding progresses due to alloy build up around the periphery of the electrode. If incremental increases are not made to the applied current in order to compensate for this, then current density will fall off resulting in production of smaller and smaller welds. Secondly, the metallic coating alloys directly to the electrode working face and metallic

alloy phases can develop. These phases can be stripped away from the electrode when the electrode is removed from the sheet surface after completion of each weld. This stripping process leaves pits or holes in the electrode face and generally erodes the electrode contact face. This is most severe when welding ZINCALUME[®] steel followed by GALVABOND[®] steel, ZINCANNEAL[®] steel and least severe with ZINCSEAL[®] steel. It is important that these effects are minimised through selection of appropriate parameters in order to extend electrode life.

Figure 1: Truncated cone electrode tip profile

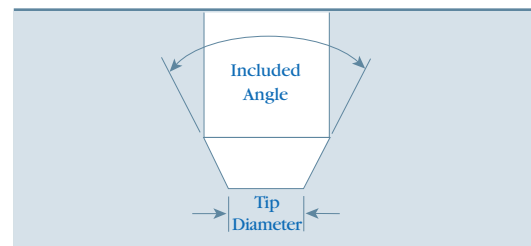

THE EFFECT OF WELDING CURRENT UPSLOPE

Upsloping is the term given to gradually increasing the welding current to the maximum preset level during spot welding rather than instantaneously applying the maximum preset current. Through the addition of a few extra cycles of welding time in current upslope, electrode life is extended considerably when welding both ZINCANNEAL[®] steel and ZINCSEAL[®] steel. Upsloping has the tendency to remove some of the metallic coating prior to the application of the maximum preset current. This assists the electrode to bed-in to the sheet surface and means that less coating is available for alloying to take place. There is no added benefit in using upsloping when welding ZINCALUME[®] steel or GALVABOND[®] steel.

THE EFFECT OF ELECTRODE TIP ANGLE

Decreasing the electrode tip included angle (see Figure 1) benefits electrode life when welding all BlueScope Steel Limited metallic coated steels. Decreasing the included angle from the commonly employed 120° angle to 90° is believed to assist in removing the alloy build-up around the periphery of the electrode tip due to the sharper angle of

incidence with the sheet surface. It is not recommended however that included angles less than this be employed since mechanical strength of the electrode tip may be lost.

THE EFFECT OF ELECTRODE TIP DIAMETER

Selection of the electrode tip face diameter depends upon the weld size desired, sheet thickness and, in some cases, design of the component (flange widths). It should be noted that electrode alignment becomes more difficult with increasing tip diameter and that even the slightest misalignment may result in metal expulsion from the sheet surface scarring the workpiece and damaging the electrodes. It is important then not to employ electrode tip diameters well beyond recommended sizes. These are usually in the region of $5\sqrt{t}$ to $6\sqrt{t}$ where t is the thickness of a single steel sheet.

Only electrodes that are used to weld ZINCALUME® steel may benefit by way of increased life with increasing tip diameter. With larger tip diameters the increase in life can be up to four-fold. The mechanisms for this are not yet clearly understood.

Using tip diameters beyond those recommended for GALVABOND® steel, ZINCANNEAL® steel and ZINCSEAL® steel result in inefficient use of welding power which is uneconomical.

THE EFFECT OF ELECTRODE CHEMISTRIES

Resistance Welder Manufacturers Association Class II (Cu-0.8%-Cr) electrode composition also referred to as J47 alloy, is the most commonly used in Australian manufacturing industries. Other compositions are also

available including Cu/Cr and Cu/Cr/Zr. While the Class II electrode composition is suitable for spot welding ZINCALUME® steel, GALVABOND® steel, ZINCANNEAL® steel and ZINCSEAL® steel, electrode life can be extended when welding ZINCANNEAL® and ZINCSEAL® steel using the Cu/Cr/Zr electrode composition. The more aggressive nature of the electrode erosion process encountered during welding of ZINCALUME® steel and GALVABOND® steel appears to outweigh any influence that electrode alloying elements may have on electrode life. The iron-rich zinc coating on ZINCANNEAL® steel and ZINCSEAL® steel however, being far less aggressive on electrodes, takes full advantage of the Cu/Cr/Zr electrode composition. Al₂O₃ dispersion strengthened copper alloy will also extend electrode life considerably but is more costly.

These features are summarised below.

Steel Type	Use Current Upslope	Use 90° Included Tip Angle	Use Increased Tip Diameters	Electrode Chemistry
ZINCALUME®	No	Yes	Yes	Cu/Cr
GALVABOND®	No	Yes	No	Cu/Cr
ZINCANNEAL®	Yes	Yes	No	Cu/Cr or Cu/Cr/Zr
ZINCSEAL®	Yes	Yes	No	Cu/Cr or Cu/Cr/Zr

To assist in the weld set-up procedure, the table below (Table 1) provides recommended spot welding practice for hot-dip zinc-coated steel sheet. These conditions are provided only as a guide. Fine tuning will be necessary to achieve optimum parameters. Note also that for ZINCANNEAL® and ZINCSEAL® zinc-iron alloy coated steels, the addition of upslope where possible is recommended.

Table 1: Recommended spot welding practice for hot-dip zinc-coated steel sheet

Steel base thickness (mm)	Electrode diameter (1)		Net electrode force (kN)	Weld time (2) (cycles)	Weld current (1000 A)	Minimum contact overlap (mm)	Minimum weld spacing (mm)	Approximate shear strength (kN)
	Body D (mm)	Tip** d (mm)						
0.40	16	3	1.5	5	8	10	10	1.2
0.50	16	4	1.8	6	9	10	10	2.2
0.60	16	4	2.0	7	9	10	10	3.1
0.80	16	5	2.5	9	11	10	15	5.4
1.0	16	5	3.0	12	12	15	15	6.8
1.2	16	6	3.6	14	13	15	20	8.6
1.6	20	7	5.0	19	16	15	25	12.2
2.0	20	8	6.6	25	19	15	30	16.0
2.5	20	9*	9.3	35	24	20	40	20.6
3.0	22	10*	12.6	45	28	20	45	25.1

* Electrode tip diameter based on approximately $6\sqrt{t}$ where t = sheet thickness

** Tip life may be increased with increasing tip diameter for ZINCALUME® zinc/aluminium alloy coated steel


SOME DO'S AND DON'TS

DO take care in machining of electrode working faces. Ensure they are relatively flat and smooth.

DO employ automatic electrode tip redressing tools where possible.

DO take care in accurately aligning electrodes in the welding machine to avoid producing undersized welds, damaging electrodes and scarring of workpiece surface through metal expulsion. Carbon paper placed between blank sheets of paper as shown below can be used to obtain an impression of electrode faces. Once in the welding machine, the electrodes can be brought together with the paper in between. The resulting impression will indicate alignment.


Impression should be circular and at same diameter as the electrode. If not, adjust alignment. Ensure welding current is turned off during this procedure.

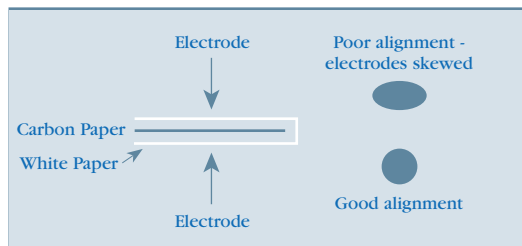


DO try and work within the welding lobe window for the particular steel type, but just below the point of metal expulsion.

SETTING THE WELD TIME

Weld time is measured in cycles. In optimising electrode life when welding metallic coated steels, weld time is chosen at a point in the middle of the "Welding lobe" as shown below. Weld time increases as material thickness increases and the lobe will shift.

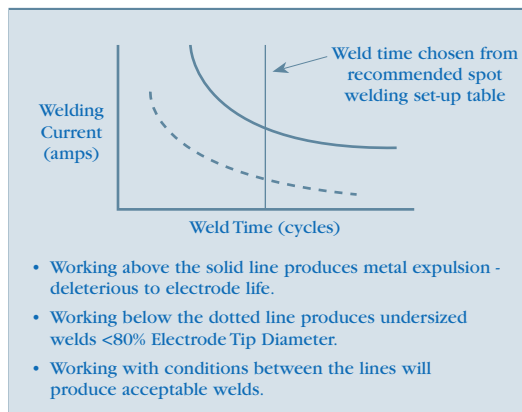

ESTABLISHING OPTIMUM CURRENT

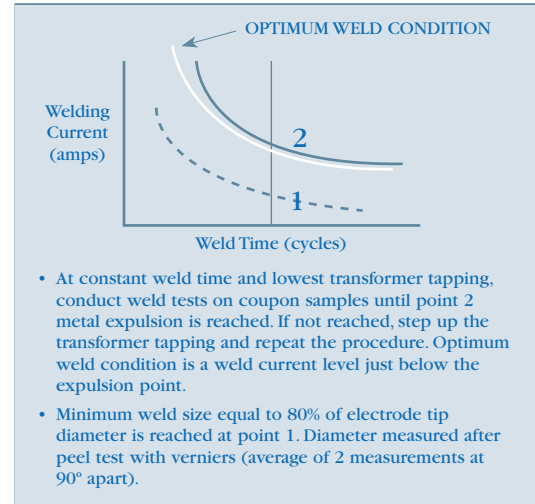

DO conduct regular inspection of weld quality and replace or redress electrodes as necessary. A simple peel test on offcuts should suffice.

DONT use hand files to redress worn electrodes. This will promote electrode misalignment.

DONT use excessive welding current. Electrode/metallic coating alloying rates will be accelerated and metal expulsion will further degrade the electrode.

DONT use excessively long welding times. It is far better to use short weld times and to adjust the welding current for optimisation of weld size.

DONT use radiused electrodes unless part fit-up is a problem. Radiused electrodes degrade more quickly than truncated electrodes when used on metallic coated steels.

WELDING FUME

It is the employer's responsibility to ensure that a suitable and sufficient assessment is made of the risk to health created by welding fume. Since no arc is used in resistance spot welding, it is considered a low fume level welding process. It is advisable however, when welding zinc-coated steels under a production type of environment, to conduct a fume assessment and where necessary, install suitable ventilation/extraction equipment to reduce risk. The Welding Technology Institute of Australia's Fume Minimisation Guidelines publication will assist in workplace fume assessment.

Note also that Material Safety Data Sheets for BlueScope Steel's metallic coated products are available on the internet at: www.bluescopesteel.com.au (see Technical Library)

The information and advice contained in this Bulletin is of a general nature only, and has not been prepared with your specific needs in mind. You should always obtain specialist advice to ensure that the materials, approach and techniques referred to in this Bulletin meet your specific requirements.

BlueScope Steel Limited makes no warranty as to the accuracy, completeness or reliability of any estimates, opinions or other information contained in this Bulletin, and to the maximum extent permitted by law, BlueScope Steel Limited disclaims all liability and responsibility for any loss or damage, direct or indirect, which may be suffered by any person acting in reliance on anything contained in or omitted from this document.

ZINCALUME[®], COLORBOND[®], GALVABOND[®], ZINCANNEAL[®] and ZINCSEAL[®] are registered trade marks of BlueScope Steel Limited.

BlueScope is a trade mark of BlueScope Steel Limited.

Please ensure you have the current Technical Bulletin as displayed at www.bluescopesteel.com.au

BlueScope Steel

Copyright[©] 2004 BlueScope Steel Limited
BlueScope Steel Limited ABN 16 000 011 058
BlueScope Steel (AIS) Pty Ltd ABN 19 000 019 625



AUSTRALIA	SYDNEY	Telephone: (02) 9795 6700
	MELBOURNE	Telephone: (03) 9586 2222
	BRISBANE	Telephone: (07) 3845 9300
	ADELAIDE	Telephone: (08) 8243 7333
	PERTH	Telephone: (08) 9330 0666

OVERSEAS	BlueScope Steel (Malaysia) Sdn Bhd	Telephone: (603) 3250 8333
	BlueScope Steel (Thailand) Limited	Telephone: (66 38) 685 710
	PT BlueScope Steel Indonesia	Telephone: (62 21) 570 7564
	BlueScope Steel Southern Africa (Pty) Limited	Telephone: (27 21) 555 4265

